

EXPERIMENTAL STUDIES OF COMBINED EXTRUSION OF PARTS MADE OF ENAW-1050A ALLOY

THOMAS Piotr

Department of Applied Computer Science and Armament Engineering, Faculty of Mechatronics and Machine Design, Kielce University of Technology, Kielce, Poland, EU

Abstract

The paper presents the results from experimental studies of combined extrusion of ENAW-1050A alloy parts. The studies were divided into three stages depending on the relative strain value of the material extruded in forward direction, ε_1 : 0.77, 0.69 and 0.59. For each value of the relative strain ε_1 , different values of relative strain of material extruded in backward direction were used: $\varepsilon_2 = 0.36, 0.46$ and 0.58 . On this basis, the influence of the relative strain level in the material extruded in forward and backward directions on the die loading force was determined. It was demonstrated that in the combined extrusion, the loading forces on the die increase with the higher levels of relative strain of material extruded in both directions. For combined extrusion, the loading forces are smaller than during the forming of the extrusions in two procedures, where in the first procedure, the cylindrical part is extruded in forward direction and in the other procedure, the sleeve part is extruded in the backward direction. Combined extrusion reduces the effort necessary to manufacture a product and the cost of manufacturing the tools whose durability is additionally enhanced due to lower values of exerted loading force.

Keywords: Aluminum, combined extrusion.

1. INTRODUCTION

In recent years, aluminum and its alloys have become widely applied materials in a number of sectors. Their excellent mechanical properties and low specific mass are deciding factors for designers in aeronautics, aerospace and automotive industries [1,2,3]. Technological advancement of the last decade has allowed manufacturers to use these materials in car subassemblies [4]. Extensive research is being conducted on designing aluminum-based materials with contemplated qualities and on developing new metal forming technologies or improving existing ones [5,6,7]. The results of the research and new solutions found are becoming crucial to industry.

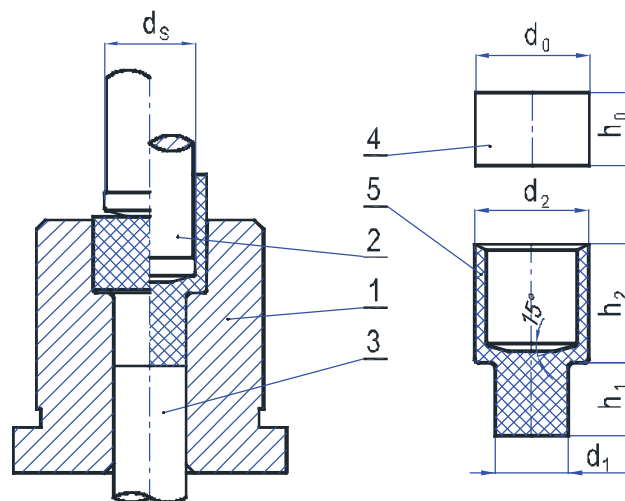


Fig. 1 The scheme of combined extrusion of aluminum stampings using conical punch:
1 - die; 2 - flat-conical punch; 3 - ejector; 4 - billet; 5 - die stamping

One of the technologies used in manufacturing products from non-ferrous metals is extrusion. Three basic techniques are used: forward, reverse and combination. The combination extrusion combines forward and backward types. The diagram of the combined extrusion is shown in **Fig. 1**.

From among a body of literature, the most comprehensive and detailed reports on extrusion can be found in [8,9]. The available literature offers analytical solutions, experimental research findings, and recommendations for process design, all relating to forward and backward extrusion only [10,11]. As the literature on combination extrusion is scarce, it has been deemed necessary to undertake studies on the subject, focusing on the analysis of loading forces in the combination extrusion process.

2. METHODS AND TEST RESULTS

The objective of this study is to perform experiments relating to combination extrusion of aluminum parts for varied values of relative strain in forward and backward directions. The experimental studies of the combination extrusion process were conducted on the test unit composed of a ZD 100 testing machine with 1 MN impact, combination extrusion tool, and a computer station with the program for measuring plastic forming forces and displacements. The combination extrusion die set was developed based on the backward extrusion die. The test unit was modernized to suit the contemplated needs by designing and manufacturing punch retainers, die holders, punches, die inserts, ejectors, columns and guide sleeves. These changes allowed producing extrusions with a sleeve-cylinder shape. As the slug for the combination extrusion process, aluminum discs A1 99.5% (ENAW-1050A) were used, softened, with external diameter $d_0=24.95\text{mm}$ and height $h_0=16\text{mm}$. **Table 1** shows the mechanical properties of the feedstock used in the tests. The material properties were determined based on the results of the static tensile test conducted to PN-EN 10002-1+AC1 [12].

Table 1 Aluminum A1 99.5% (ENAW-1050A) properties.

Material	$R_{0.2}$	R_m	A	$A_{11.3}$	Z
A1 99.5%	24MPa	82MPa	46%	34%	86%

The experimental studies were carried out for flat die inserts, with punches with bullet-shaped nose and the punch front part inclination angle of 15° . The dimensions of the extrusions were the following:

- for the upper part of the extrusion formed in backward direction, external diameter $d_2=25\text{mm}=\text{const}$, while internal diameters (punch diameter) $d_s=15, 17, \text{ and } 19\text{mm}$,
- diameters of the bottom part of the extrusion formed in forward direction are $d_1=12, 14 \text{ and } 16\text{mm}$, respectively.

The assumed dimensions of the input material and extrusions allowed obtaining the following degrees of relative strains:

- consecutively for the backward extrusion
- $\varepsilon_2=d_s^2/d_0^2=0.36; 0.46; 0.58$ (1)

- for forward extrusion
- $\varepsilon_1=(d_0^2-d_1^2)/d_0^2=0.77; 0.69; 0.59$. (2)

The increase in the relative strain ε_2 in the backward direction reduced the thickness of the extrusion sleeve part, whereas the decrease in strain ε_1 led to the increase in the cylindrical part of the extrusion in the forward direction. It was assumed that the maximum height of the cylindrical part of the extrusion formed in forward extrusion was $h_1 = 14\text{mm}$ due to the design of the test die. This value restricted further movement of the material in the forward direction because of the ejector used in the tests.

The tests began for the flat insert with constant relative strain $\varepsilon_1=0.77=\text{const}$ ($d_1=12\text{mm}$) in the forward direction. The use of flat-conical punches (15°) with varied diameters of the working parts allowed obtaining

various values of relative strains in the backward direction, $\varepsilon_2=0.36$; 0.46; 0.58. The tests were conducted with no lubrication applied. **Fig. 2** shows the plots of the impact applied by the punch as a function of displacement.

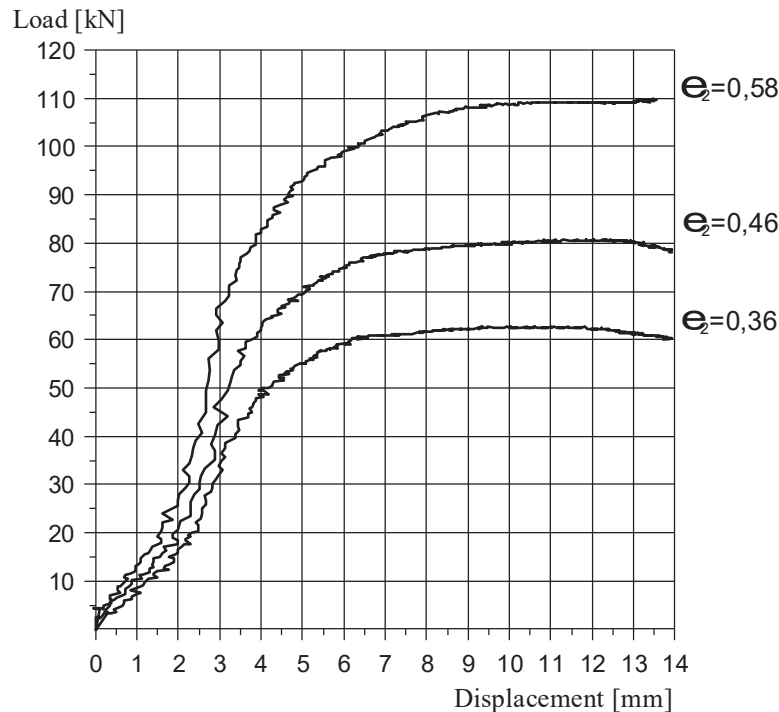


Fig. 2 The stress of the punch as a function of displacement during combined extrusion for different degrees of backward strain ε_2 and constant value of forward extrusion $\varepsilon_1=0.77$ ($d_1=12\text{mm}$)

The traces of forces shown in **Figs. 3** and **Figs. 4** were plotted for different relative strains ε_1 in the forward direction. In **Fig. 3**, the strain value was taken to be $\varepsilon_1=0.69$ ($d_1=14\text{mm}$), with $\varepsilon_1=0.59$ ($d_1=16\text{mm}$) in **Fig. 4**, which was possible owing to increased diameter of the die insert d_1 from $\varnothing 12\text{ mm}$ to $\varnothing 14\text{mm}$ and $\varnothing 16\text{mm}$, respectively.

The extrusion process was conducted for the punch displacement $s=14\text{mm}$. The final displacement measurement was made using a dial indicator, whose plunger moved perpendicularly to the bottom surface of the upper die plate. This allowed the measurement of the end part of the punch displacement to an accuracy of 0.01mm. Ending the process earlier was associated with reaching the ejector by the material moving in the forward direction, which caused a rapid rise in loading force. From this moment the extrusion process would be conducted as backward extrusion.

The analysis of forces presented in **Figs. 2, 3 and 4** indicates that in the first stage of the combination extrusion process, a rapid gain in loading force occurs as a function of the punch displacement. Then, the forces become stable. For $\varepsilon_2=0.36$, in the final stage of the process, the forces decrease irrespective of the value of relative strain ε_1 in the forward direction. It is also obvious that the drop in the punch loading force at the final stage is higher for lower values of relative strains ε_1 in the forward direction (**Fig. 3** and **Fig. 4**, $\varepsilon_2=0.36$). For $\varepsilon_2=0.58$ in the final stage of the extrusion process, a rise in the loading forces is observed for relative strain $\varepsilon_1=0.77$ and $\varepsilon_1=0.69$.

In combination extrusion, the increased relative strain ε_2 in the backward direction leads to the increase in loading force. For $\varepsilon_1=0.77$ and $\varepsilon_2=0.36$ (**Fig. 2**), the maximum loading force is 62kN. Increased relative strain

ε_2 in the backward direction causes the values of the forces to rise by 30% (for $\varepsilon_2=0.46$) and 76% (for $\varepsilon_2=0.58$). Increased loading force results from greater hardening of the material.

In combination extrusion, a significant influence on the value of loading forces at the same relative strain ε_2 in the backward direction is exerted by strain ε_1 in the forward direction. For $\varepsilon_2=0.46=\text{const}$ and $\varepsilon_1=0.59$, the maximum loading force is 73kN (**Fig. 4**). Increasing the relative strain ε_1 from 0.59 to 0.69 and 0.77 at $\varepsilon_2=0.46=\text{const}$ results in the increase in the maximum loading force of 6 % (**Fig. 3**) and 11 % (**Fig. 2**).

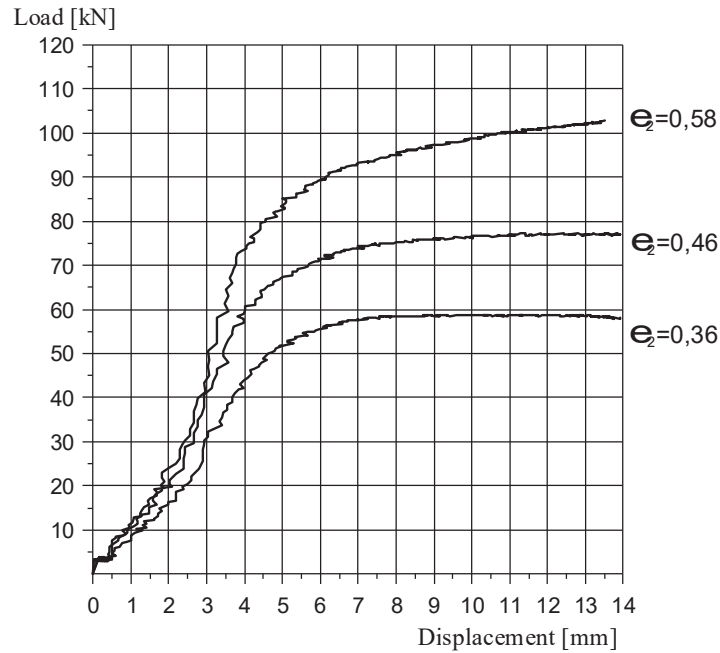


Fig. 3 The stress of the punch as a function of displacement during combined extrusion for different degrees of backward strain ε_2 and constant value of forward extrusion $\varepsilon_1=0.69$ ($d_1=14\text{mm}$).

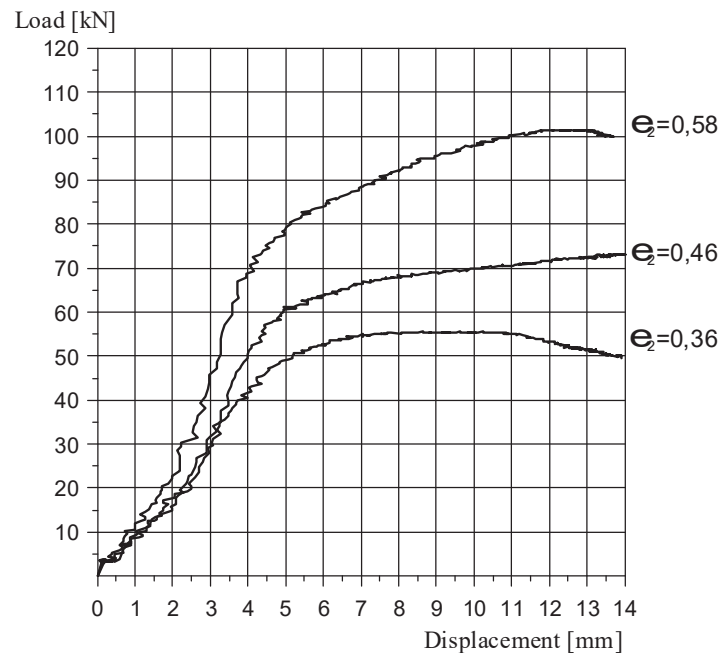


Fig. 4 The stress of the punch as a function of displacement during combined extrusion for different degrees of backward strain ε_2 and constant value of forward extrusion $\varepsilon_1=0.59$ ($d_1=16\text{mm}$).

3. CONCLUSION

The following conclusions can be drawn based on the findings from the tests conducted on aluminum parts extruded in combination extrusion. The increase in relative strain ε_2 in the backward direction causes higher loading forces. The increase in diameter d_1 of the die insert and thus reducing relative strain ε_1 in the forward direction causes reduction in the loading forces for the same values of relative strains ε_2 . Note that the results from the experimental studies presented here showed the advantages of the combination extrusion process relative to forward and backward extrusion processes, as well as expanded the knowledge of the combination extrusion process. Forming of products in combination extrusion eliminates the need to conduct two operations, where the cylindrical part of the extrusion is made in the forward extrusion process and the sleeve part of the extrusion is made in the backward extrusion process. Combination extrusion reduces the cost and effort necessary to manufacture the tools and has a significant positive influence on the durability of the tooling.

REFERENCES

- [1] BRANDT D. Konstruieren mit Aluminum Schmiedestücken, Designing with Aluminum Forgings, Umformtechnik, Vol. 26, No 3, 1992.
- [2] DOM F.J. Meltspun aluminum successful in racing pistons, Aluminum, Vol. 70, Nr. 9/10, 1994, pp. 575-578.
- [3] GABATHULER J.P. Formed Components for the Car Industry, Aluminum, Vol. 73, No. 5, 1997.
- [4] Neues Aluminumrohr Speziell für KFZ-Konstruktionen, Aluminum, t. 80, Nr 6, 2004.
- [5] THOMAS P. Experimental investigation of combined extrusion of aluminum products for different shapes of die inserts", 10th European Conference of Young Researchers and Scientists Transcom 2013, Žilina, pp. 199-202.
- [6] THOMAS P. Influence of manner of extrusion on the stress forces of the extrusion of different sized aluminum stampings. Terotechnologia 2013, Kielce, pp. 251-259.
- [7] THOMAS P., CHAŁUPCZAK J. Research and analysis of stress force in combined extrusion for different shapes of die stampings. Rudy i Metale Nieżelazne. R-53, 2008, nr 11, pp. 726-730.
- [8] LANGE K. Handbook of Metal Forming, McGraw-Hill Book Company 1985.
- [9] ERBREL S., KUCZYŃSKI K. Selected issues of shaping geometrical bodies. Part II. Polish Engineers and Technicians Association. Personnel Development Centre. Warsaw 1989.
- [10] LEŚNIAK D., RĘKAS A., LIBURA W., ZASADZIŃSKI J. Numerical investigations of welding conditions during extrusion of 2024 alloy through porthole dies. Key Engineering Materials, 2012 vol. 491, pp. 205-213.
- [11] ZASADZIŃSKI J., RĘKAS A., LIBURA W., RICHERT J., LEŚNIAK D. Numerical analysis of aluminum alloys extrusion through porthole dies. Key Engineering Materials 2010 vol. 424, pp. 105-111.
- [12] PN-EN 10002-1+AC1 Tension Test.